



RETRACTED: Effect of Bimetal Element Doping on the Low-Temperature Activity of Manganese-Based Catalysts for NH₃-SCR

Haixia Li*, Shuaibo Zhang, Anchao Zhang*, Xinmin Zhang, Zhijun Sun, Changze Yang and Qifeng Zhu

School of Mechanical and Power Engineering, Henan Polytechnic University, Jiaozuo, China

OPEN ACCESS

Edited by:

Xiaohang Zheng,
Harbin Institute of Technology, China

Reviewed by:

Andrew Ng Kay Lup,
Xiamen University, Malaysia
Shule Zhang,
Nanjing University of Science and
Technology, China

*Correspondence:

Haixia Li
lihx@hpu.edu.cn
Anchao Zhang
anchaozhang@126.com

Specialty section:

This article was submitted to
Inorganic Chemistry,
a section of the journal
Frontiers in Chemistry

Received: 30 May 2022

Accepted: 23 June 2022

Published: 22 July 2022

Citation:

Li H, Zhang S, Zhang A, Zhang X,
Sun Z, Yang C and Zhu Q (2022) Effect
of Bimetal Element Doping on the Low-
Temperature Activity of Manganese-
Based Catalysts for NH₃-SCR.
Front. Chem. 10:957051.
doi: 10.3389/fchem.2022.957051

A series of novel Mn₆Zr_{1-x}Co_x denitrification catalysts were prepared by the co-precipitation method. The effect of co-modification of MnO_x catalyst by zirconium and cobalt on the performance of NH₃-SCR was studied by doping transition metal cobalt into the Mn₆Zr₁ catalyst. The ternary oxide catalyst Mn₆Zr_{0.3}Co_{0.7} can reach about 90% of NO_x conversion in a reaction temperature range of 100–275°C, and the best NO_x conversion can reach up to 99%. In addition, the sulfur resistance and water resistance of the Mn₆Zr_{0.3}Co_{0.7} catalyst were also tested. When the concentration of SO₂ is 200ppm, the NO_x conversion of catalyst Mn₆Zr_{0.3}Co_{0.7} is still above 90%. 5 Vol% H₂O has little effect on catalyst NO_x conversion. The results showed that the Mn₆Zr_{0.3}Co_{0.7} catalyst has excellent resistance to sulfur and water. Meanwhile, the catalyst was systematically characterized. The results showed that the addition of zirconium and cobalt changes the surface morphology of the catalyst. The specific surface area, pore size, and volume of the catalyst were increased, and the reduction temperature of the catalyst was decreased. In conclusion, the doping of zirconium and cobalt successfully improves the NH₃-SCR activity of the catalyst.


Keywords: NH₃-SCR, sulfur resistance, nitrogen oxide, metal modification, low temperature

HIGHLIGHTS

- The ternary oxide catalyst Mn₆Zr_{0.3}Co_{0.7} catalyst was prepared by the co-precipitation method.
- The NO_x conversion of the Mn₆Zr_{0.3}Co_{0.7} catalyst is above 90% at 100–275°C.
- The Mn₆Zr_{0.3}Co_{0.7} catalyst has excellent resistance to H₂O and SO₂.
- The Mn₆Zr_{0.3}Co_{0.7} catalyst has a large specific surface area and pore diameter.
- The reaction mechanism of the Mn₆Zr_{0.3}Co_{0.7} catalyst was investigated.

INTRODUCTION

With continuous exploitation and utilization of fossil fuels, serious pollution has been caused to the atmosphere, among which nitrogen oxide (NO_x) is one of the most important pollutants. Therefore, the removal of NO_x is particularly important. At present, the most effective method for NO_x removal

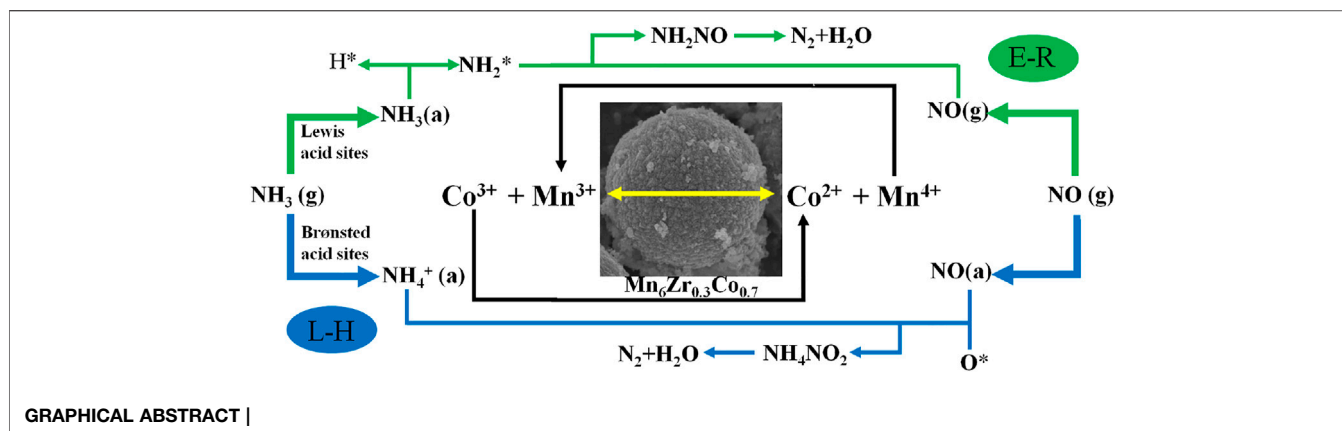


is selective catalytic reduction of NO_x with NH₃ (NH₃-SCR) (Zhang et al., 2015; Hu et al., 2017). In recent years, commercial SCR catalysts including V₂O₅/TiO₂-WO₃ and V₂O₅/TiO₂-MoO₃ had excellent deoxidation activity. However, because of the narrow operating temperature window, the activity of the catalyst is poor at low temperatures, and it can only work at high temperatures (350–450°C). In this way, the denitration device can only be installed at the front end of the desulfurization device, while the presence of SO₂ in the flue gas can lead to V₂O₅/TiO₂ catalyst inactivation (Shi et al., 2011; Hu et al., 2018). Therefore, the denitrification device can only be installed downstream of the desulfurization device, but this cannot meet the optimal reaction temperature of the V₂O₅/TiO₂ catalyst (Jin et al., 2022). At the same time, the V₂O₅/TiO₂ catalyst may also cause vanadium poisoning (Kwon et al., 2016; Hu et al., 2018). To sum up, it is particularly important to develop a kind of low-temperature and high-activity catalyst.

At present, the most widely studied catalysts are transition metal catalysts, zeolite catalysts, and rare earth metal catalysts. Among transition metal catalysts, manganese oxide (MnO_x) catalysts have attracted much attention due to their excellent low-temperature SCR performance. However, the working temperature window of pure MnO_x catalyst is narrow, and when there is SO₂ and H₂O in the flue gas, the MnO_x catalyst will be inactivated, which seriously affects the denitration activity. Therefore, it is necessary to widen the temperature window of the MnO_x catalyst and improve the water and sulfur resistance. The Mn-Ce binary oxide catalyst prepared by the solvothermal method has abundant chemisorption oxygen and active sites and shows excellent low-temperature activity and significant sulfur resistance (Chen et al., 2021). Tang prepared Mn-Fe-Ce_{0.1} ternary oxide catalyst by the co-precipitation method, which has a large specific surface area and strong surface acidity, which is conducive to enhance the SCR denitration activity of the catalyst and improving the resistance to SO₂ and H₂O (Tang et al., 2020). In addition, MnAlO_x (Zhou et al., 2019), Fe-Mn/Al₂O₃ (Wang et al., 2016), and Mn/TiWO_x (Chen et al., 2016a) have excellent SCR activity and water and sulfur resistance. Therefore, the introduction of one or more metal elements in the MnO_x

catalyst can enhance the physicochemical properties of MnO_x catalyst so that the prepared catalyst has excellent denitrification performance.

Zirconium additives can improve the dispersity and activity of the catalyst and the sulfur resistance of the catalyst (Kantcheva et al., 2011). Ali synthesized the Cu_xCe_{0.5-x}Zr_{0.5} oxide catalyst by the citric acid method, which showed excellent SCR activity, N₂ selectivity, and water and sulfur resistance (Ali et al., 2017). Doped zirconium into the Cr₂O₃ catalyst by the co-precipitation method, which changed the surface performance of chromium oxide catalyst, improved the acid position of the CrZrO₃ catalyst, the concentration of surface adsorbed oxygen O_a and Cr⁶⁺, and improved the SCR performance of the catalyst (Guo et al., 2021). In addition, Hu reported the influence of Co₃O₄ doping on NH₃-SCR reaction in manganese-based catalyst, which greatly improved the redox capacity of the catalyst and proposed the reaction mechanism (Hu et al., 2015). Gao added cobalt to MnO_x through complexation esterification, and the catalyst showed good activity and improved the resistance of MnO_x to SO₂ (Gao et al., 2018). Zhang found that Mn_xCo_{3-x}O₄ nanocages prepared by self-assembly have higher N₂ selectivity, wider operating temperature range, and better SO₂ tolerance compared with nanoparticles (Zhang et al., 2014). Therefore, the doping of zirconium and cobalt in manganese catalysts is of great research value.

In view of the reported effect of zirconium and cobalt on improving the catalytic activity and sulfur resistance of manganese-based catalysts, bimetal elements of zirconium and cobalt were added to the manganese-based catalysts simultaneously in the hope of preparing a more efficient denitration catalyst. In this study, a series of related Mn₆Zr_{1-x}Co_x catalysts were prepared by the co-precipitation method. The effects of cobalt-doped Mn₆Zr₁ bilayer oxides on the activity and resistance to SO₂ and H₂O were studied. In addition, the denitrification activity was tested in a fixed-bed reactor. The physicochemical properties of catalysts were investigated by conducting a series of related experiments and characterization, such as temperature-programmed technology, SEM, XRD, BET, XPS, H₂-TPR, NH₃-TPD, and *In Situ* DRIFTS.

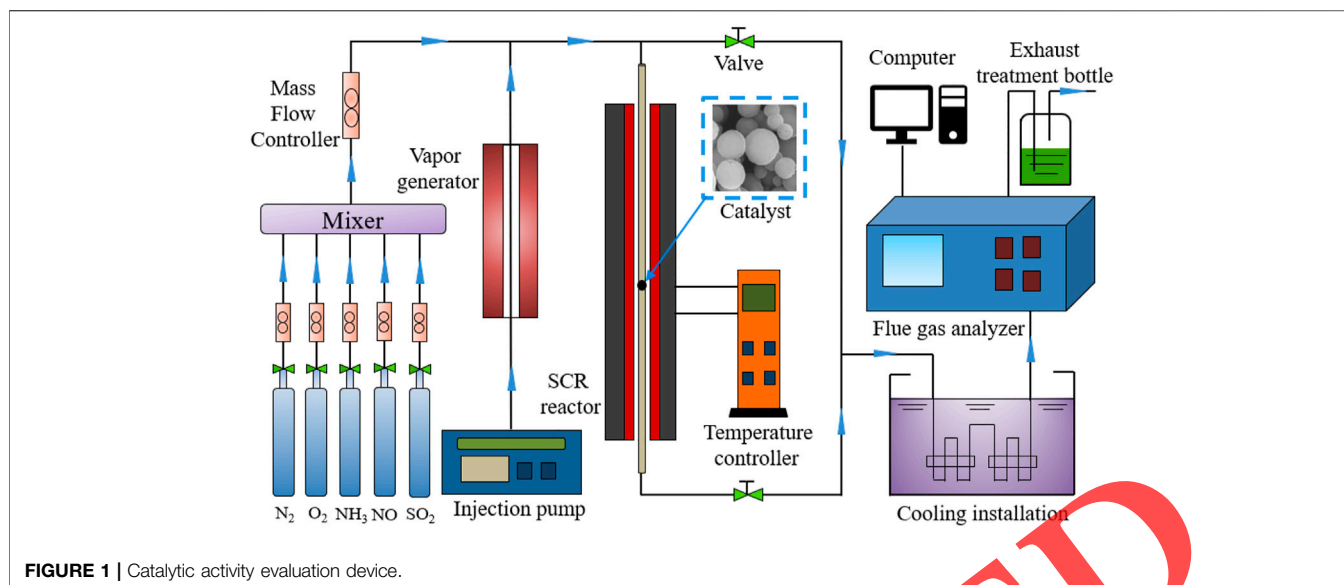

EXPERIMENTAL

Materials

All samples were synthesized by the co-precipitation method with $\text{Mn}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ (99.0%, Macklin, Shanghai), $\text{Zr}(\text{NO}_3)_4 \cdot 5\text{H}_2\text{O}$ ($\geq 99.0\%$, Macklin, Shanghai), and $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ($\geq 99.0\%$, Macklin, Shanghai). NaOH ($\geq 96.0\%$, Macklin, Shanghai) was used to regulate pH. $(\text{NH}_4)_2\text{CO}_3$ ($\geq 40.0\%$, MACKLIN, Shanghai) was used as the precipitator. In this study, none of the reagents used needs to be further purified.

Catalyst Preparation

A series of $\text{Mn}_6\text{Zr}_{1-x}\text{Co}_x$ catalysts were prepared by the co-precipitation method. Specifically, the corresponding precursor material was weighed, in which Mn: (Zr + Co) = 6:1, and the ratio of Zr: Co was 1:9, 3:7, 5:5, 7:3, and 9:1 (all ratios were molar ratios). Then, the mixed solution was put into five 300-ml beakers according to the proportion and marked with 1#, 2#, 3#, 4#, and 5#. Also, 100 ml of deionized water was added to each of the five beakers. The mixed solution was heated at 30°C in a water bath for 30 min and mixed with a magnetic stirrer at 500 r/min. 50 ml $0.5 \text{ mol L}^{-1} (\text{NH}_4)_2\text{CO}_3$ solution was gradually dropped into the abovementioned solution with full stirring for 2 h. Also, $0.5 \text{ mol L}^{-1} \text{NaOH}$ solution was gradually added to the obtained solution to keep at pH = 9. The abovementioned solutions were aged at room temperature for 24 h, and then the supernatant was removed from the beaker and the sediment was collected. The sediment was washed with deionized water until neutral pH = 7. The washed sediments were dried at 105°C by using vacuum drying oven overnight to get the primary product. The primary products were calcined at 400°C for 3 h in a muffle furnace. Finally, solids were crushed and screened to 40–60 mesh to

obtain the final experimental catalyst. Samples 1#, 2#, 3#, 4#, and 5# were $\text{Mn}_6\text{Zr}_{0.1}\text{Co}_{0.9}$, $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$, $\text{Mn}_6\text{Zr}_{0.5}\text{Co}_{0.5}$, $\text{Mn}_6\text{Zr}_{0.7}\text{Co}_{0.3}$, and $\text{Mn}_6\text{Zr}_{0.9}\text{Co}_{0.1}$, respectively.

Catalytic Performance Test


The activity of the catalyst was evaluated and detected by temperature-programmed technology, as shown in **Figure 1**. Each test used a catalyst (0.2 g, 40–60 mesh) with a volume of about 0.5 ml, which was placed in a fixed-bed quartz reactor (diameter = 9 mm, length = 60 mm) for the NH_3 -SCR activity evaluation test. The reaction gas of NH_3 -SCR denitrification consists of 500 ppm NO, 500 ppm NH_3 , 5vol% O_2 , 100–200 ppm SO_2 (when used), 5Vol% H_2O (when used), and N_2 as equilibrium gas. The total flow rate of the gas is 500 ml min^{-1} , and the gas hourly space velocity (GHSV) was about $60,000 \text{ h}^{-1}$. The reaction temperature was 100–300°C when the catalyst activity was tested. The concentrations of NO_x and O_2 before and after the reaction were measured by a flue gas analyzer. The remaining unconverted gas is filtered with sodium hydroxide solution. Each temperature point was held for 30 min, and the data were recorded in a numerical stable state. NO_x conversion and N_2 selectivity are calculated by the following equations, respectively:

$$\text{NO}_x \text{ conversion} = \frac{[\text{NO}_x]_{\text{in}} - [\text{NO}_x]_{\text{out}}}{[\text{NO}_x]_{\text{in}}} \times 100\%, \quad (1)$$

$$\text{N}_2 \text{ selectivity} (\%) = \left(1 - \frac{2[\text{N}_2\text{O}]_{\text{out}} + [\text{NO}_2]_{\text{out}} - 2[\text{N}_2\text{O}]_{\text{in}} - [\text{NO}_2]_{\text{in}}}{[\text{NH}_3]_{\text{in}} + [\text{NO}_x]_{\text{in}} - [\text{NH}_3]_{\text{out}} - [\text{NO}_x]_{\text{out}}} \right) \times 100\%. \quad (2)$$

The SCR activity of the catalyst can also be quantitatively expressed by the first-order rate constant (k), which can be calculated by the formula of NO conversion (X) as follows (Gao et al., 2014; Jiang et al., 2020).

$$k = -\frac{F_0}{[\text{NO}]_0 W} \ln(1 - X), \quad (3)$$

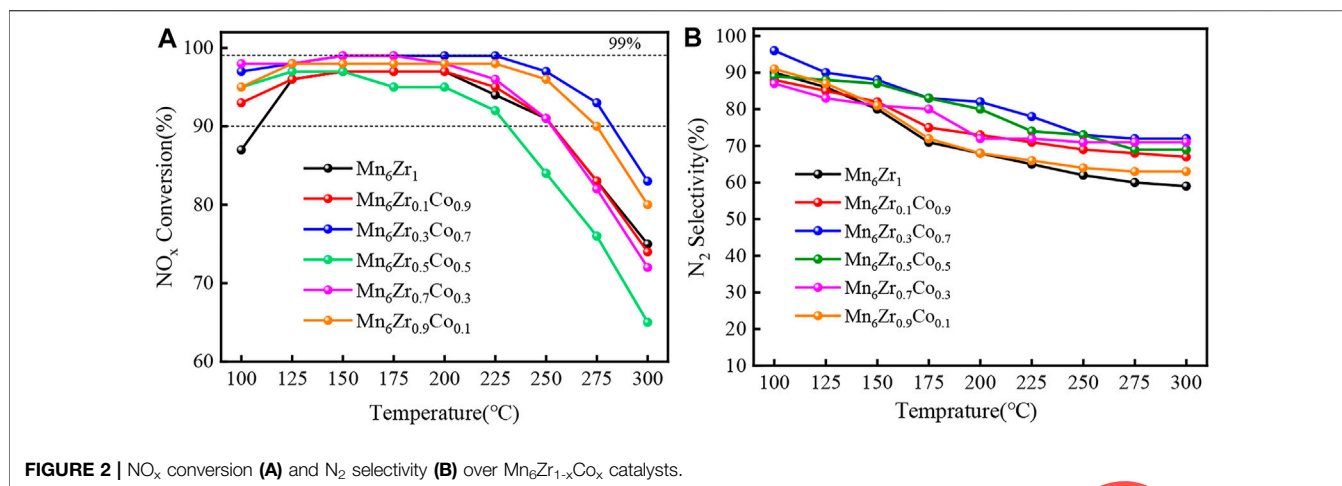

$$\ln k = -\frac{E_a}{RT} + \ln A, \quad (4)$$

where F_0 is NO feeding rate; $[\text{NO}]_0$ is NO concentration at the inlet; W is catalyst dosage; E_a is the apparent activation energy; T is the Kelvin temperature; R is the gas constant; A is the pre-exponential factor.

Catalyst Characterization



The X-ray diffraction (XRD) test was carried out with Cu-K α radiation ($\lambda = 0.15418$ nm) in a 40-kV and 40-mA X-ray tube by using a Bruker D8 Advance in Germany, and the scanning range is 10–80°. A scanning electron microscope (SEM), produced by Hitachi Company Japan, was used to analyze the morphology of the catalysts. Before the test, the sample is evenly smeared on the surface of the conductive adhesive and then sprayed with gold. The N₂ adsorption–desorption isotherms of the catalysts were determined by using Quantachrome Instruments Quadrasorb Evo with high purity N₂ as the adsorbent. Before each analysis, the catalysts were degassed in a vacuum at 300°C for 3 h, and isotherms were measured at liquid nitrogen N₂ (–196°C). The speed is 6/min. The XPS tester uses the Escalab 250XI spectrometer from Semer, Inc., operating under monochrome Al K α radiation (1486.6 eV), 12 kV, and 15 mA ultra-high vacuum, and all binding energies were calibrated by C1s peak at 284.4 eV. Temperature programmed reduction of H₂ (H₂-TPR) and temperature-programmed desorption of NH₃ (NH₃-TPD) were performed on the Mac AutoChem II 2920 instrument (United States). The former was pretreated in 300°C argon at a flow rate of 20 ml/min for 1 h and cooled to room temperature. The gas was converted into a mixture of 5Vol % H₂-N₂ at a flow rate of 30 ml/min. After a straight baseline, the catalyst was heated from room temperature to 800°C at a rate of 10°C/min. The latter was pretreated in 300°C argon at a flow rate of 20 ml/min for 1 h and cooled to room temperature. The samples were then exposed to a mixture of 5 vol% NH₃-N₂ for 1 h and then purified with high-purity He at a flow rate of 20 ml/min to remove the physically adsorbed NH₃. After the baseline was

stabilized, the sample was heated from room temperature to 800°C at a rate of 10°C/min. The *in situ* Diffuse Reflectance Infrared Transform Spectroscopy (*in situ* DRIFTS) experiments were applied on a Thermo fisher Nicolet iS50 FTIR spectrometer to characterize the desorption of NO and NH₃ on catalytic materials.

EVALUATION OF CATALYST ACTIVITY

Catalytic Activity for NH₃-SCR

All samples were tested for the catalytic performance of NH₃-SCR and the results are shown in **Figure 2A**. The NO_x conversion of all catalysts increased first and then decreased with the increase of reaction temperature. When the reaction temperature is 125–250°C, the NO_x conversion of the Mn₆Zr₁ catalyst is more than 90%, showing excellent catalytic activity. The effect of Co/Zr ratios on NH₃-SCR performance of Mn₆Zr_{1-x}Co_x catalysts is shown in **Figure 2A**. It is worth noting that the NO_x conversion first declines and then enhances with the increase of Co ratio. Among these catalysts, the Mn₆Zr_{0.3}Co_{0.7} catalyst exhibits optimal NH₃-SCR activity with the NO_x conversion being above 90% in the range of 100–275°C and 99% in the range of 150–225°C. However, the Mn₆Zr_{0.5}Co_{0.5} catalyst shows the worst NH₃-SCR activity. These findings indicate that the high same Co/Zr content does not improve the catalytic performance of NO_x conversion. This may be because the combination of zirconium and cobalt can change the physical and chemical properties of the catalyst surface, thus affecting the adsorption, redox, and surface reaction of active molecules on the catalyst surface. Meanwhile, the N₂ selectivity of all catalysts was tested, as shown in **Figure 2B**. The selectivity of N₂ decreases with the increase of reaction temperature, which may be related to the formation of N₂O on the catalyst. When the Mn₆Zr₁ catalyst is doped with cobalt, the selectivity of N₂ is obviously improved. At 100–200°C, the N₂ selectivity of the Mn₆Zr_{0.3}Co_{0.7} catalyst is above 80%, and the optimum N₂ selectivity is 96%. In conclusion, cobalt doping in the Mn₆Zr₁

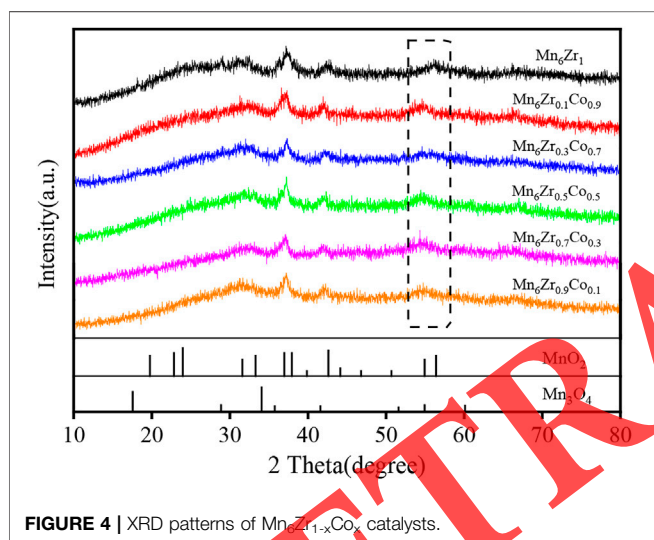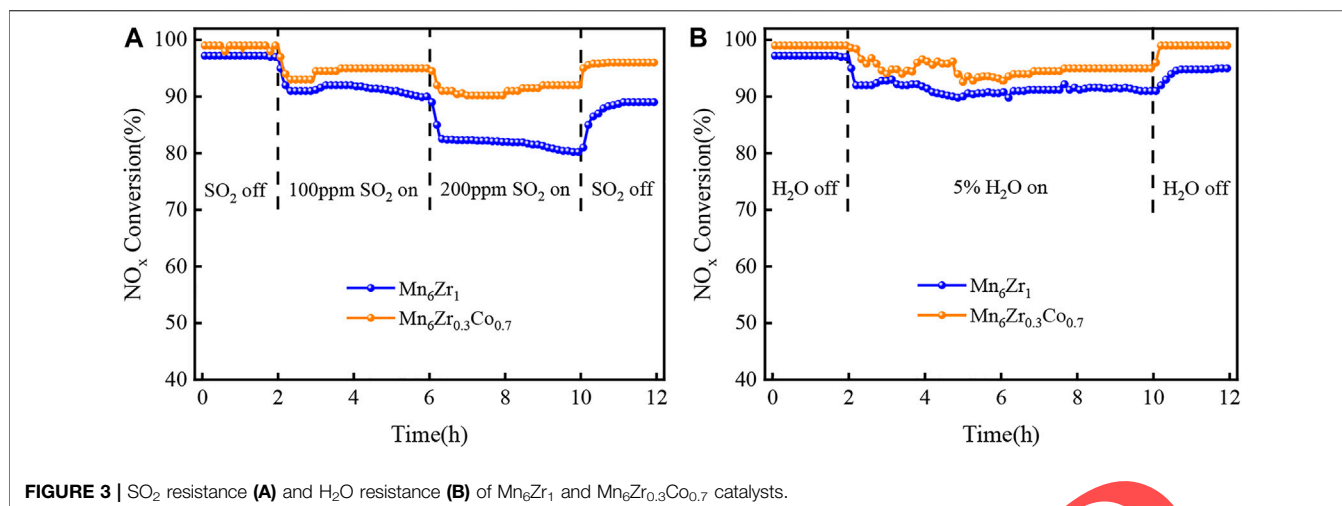

catalyst significantly enhances its catalytic activity, widens the temperature window, and improves the selectivity of N₂.

SO₂ and H₂O Tolerance Resistance of Catalyst

In order to simulate the flue gas atmosphere under the actual conditions, the denitration efficiency of the catalyst was tested under the conditions containing SO₂ or H₂O, which were all measured at the optimum reaction temperature. The NO_x conversion in the SO₂ atmosphere is shown in **Figure 3A**. The Mn₆Zr_{0.3}Co_{0.7} catalyst has significantly higher sulfur resistance than the Mn₆Zr₁ catalyst. The NO_x conversion of the Mn₆Zr_{0.3}Co_{0.7} catalyst stabilized at 95% after 4 h when 100 ppm SO₂ was injected into the simulated flue gas. The NO_x conversion of the Mn₆Zr_{0.3}Co_{0.7} catalyst remains above 90% when 200 ppm SO₂ is added. The results indicated that cobalt doping in the Mn₆Zr₁ catalyst significantly improved its

resistance to sulfur. The main reason may be that cobalt doping into the Mn₆Zr₁ catalyst increases the active sites on the catalyst surface and changes the physicochemical properties and redox performance of the catalyst. In addition, the NO_x conversion of two kinds of catalyst did not recover to the initial NO_x conversion after the SO₂ was turned off, mainly because SO₂ and NH₃ reaction formation sulfate or metal oxides are difficult to decompose under low-temperature, which covers some active sites on the catalyst and acid sites, and the activity cannot recover to the original SCR catalysts (Jia et al., 2018). At the same time, the water tolerance test of the catalyst was measured under the condition of 5Vol% H₂O, and the results are shown in **Figure 3B**. The results showed that when 5Vol% H₂O is added to the simulated gas, the NO_x conversion of the two catalysts decreases and the conversion of the catalysts is basically stable after 8 h. The conversion of the Mn₆Zr_{0.3}Co_{0.7} catalyst is stable at 95% and that of Mn₆Zr₁ catalyst is stable at 92%. The Mn₆Zr_{0.3}Co_{0.7} catalyst showed the best water resistance, indicating that the doping of cobalt also improved the water resistance of the Mn₆Zr₁ catalyst. The NO_x conversion of the Mn₆Zr_{0.3}Co_{0.7} catalyst recovered up to 99% of the initial value after the water vapor was turned off, indicating that the catalyst was reversible.

CHARACTERIZATION ANALYSIS OF CATALYSTS

Crystal Structure Analysis

In order to understand the crystal structure of the catalysts, all the catalysts were characterized by XRD, and the results are shown in **Figure 4**. It can be seen that MnO₂(PDF#12-0141) and Mn₃O₄(PDF#04-0732) species exist on the Mn₆Zr₁ catalyst. The diffraction peaks of Mn₆Zr_{1-x}Co_x series catalysts decrease gradually with the decrease of doping cobalt content x. This indicates that MnO_x species are highly dispersed and form a microcrystalline structure on the Mn₆Zr_{1-x}Co_x catalyst, which contributes to the improvement of catalyst activity (Gong et al., 2020). In addition,

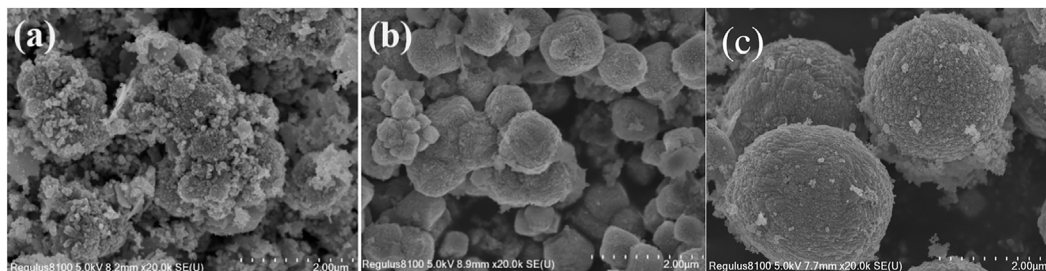


FIGURE 5 | SEM image of (A) CoO_x, (B) Mn₆Zr₁, and (C) Mn₆Zr_{0.3}Co_{0.7}.

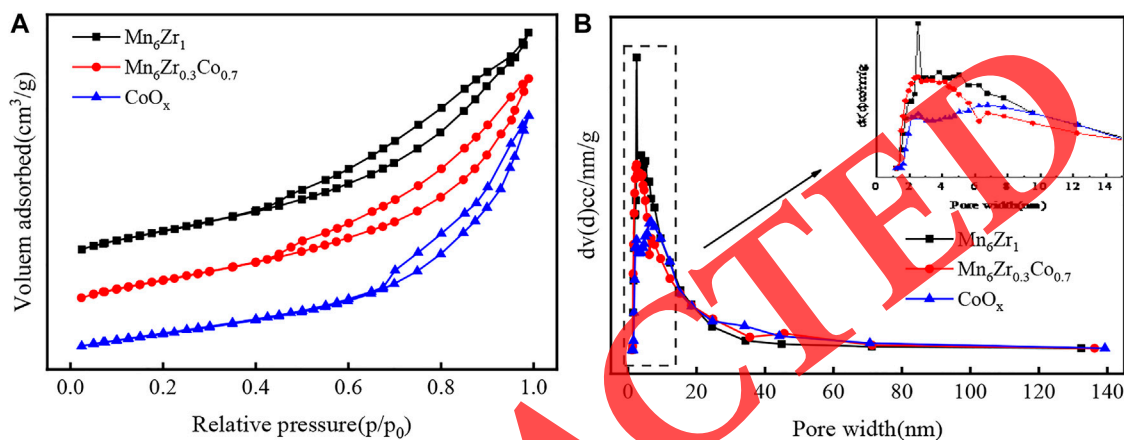


FIGURE 6 | (A) N₂ adsorption isotherms and (B) pore size distributions of Mn₆Zr₁, Mn₆Zr_{0.3}Co_{0.7}, and CoO_x.

TABLE 1 | Surface areas, pore-volume, and average pore diameter of the samples.

Samples	Surface area (m ² /g)	Pore volume (cm ³ /g)	Average pore diameter (nm)
Mn ₆ Zr ₁	153	0.28	2.5
CoO _x	109.3	0.28	6.7
Mn ₆ Zr _{0.3} Co _{0.7}	155.6	0.29	3.7

when $2\theta = 55^\circ$, there is a wide diffraction peak, which can be understood as the mixed oxide of MnO₂ and Mn₃O₄. The wide peak structure is conducive to the adsorption, desorption, and redox reaction on the catalyst surface (Tang et al., 2007). It is worth noting that the phases of ZrO₂ and CoO_x were not detected on all the catalysts, indicating that the phases related to them are likely to be introduced into the lattice of MnO_x to form a solid solution (Azalim et al., 2011).

Crystal Morphology Analysis

Figure 5 shows the SEM morphology of CoO_x, Mn₆Zr₁, and Mn₆Zr_{0.3}Co_{0.7} catalysts. As shown in Figure 5A, the morphology of CoO_x is an irregular block structure. As shown in Figure 5B,C the Mn₆Zr₁ catalyst present a cubic structure. It was found that the surface morphology of the original catalyst changed

significantly after doping cobalt. As can be seen from Figures 5D,E, the morphology of the Mn₆Zr_{0.3}Co_{0.7} catalyst changes into a spherical structure with a diameter of 26 μm. In addition, Figure 5F clearly shows that the surface of Mn₆Zr_{0.3}Co_{0.7} catalyst forms a villous structure of about 1 μm. Such villi increase the specific surface area of the catalyst and the active sites on the surface. In the SCR denitration process, the reaction molecules can be captured better, thus promoting the denitration activity of the catalyst.

Specific Surface Area and Pore Structure Analysis

Figure 6 shows the N₂ adsorption isotherms and pore size distribution of the three catalysts of Mn₆Zr₁, CoO_x, and

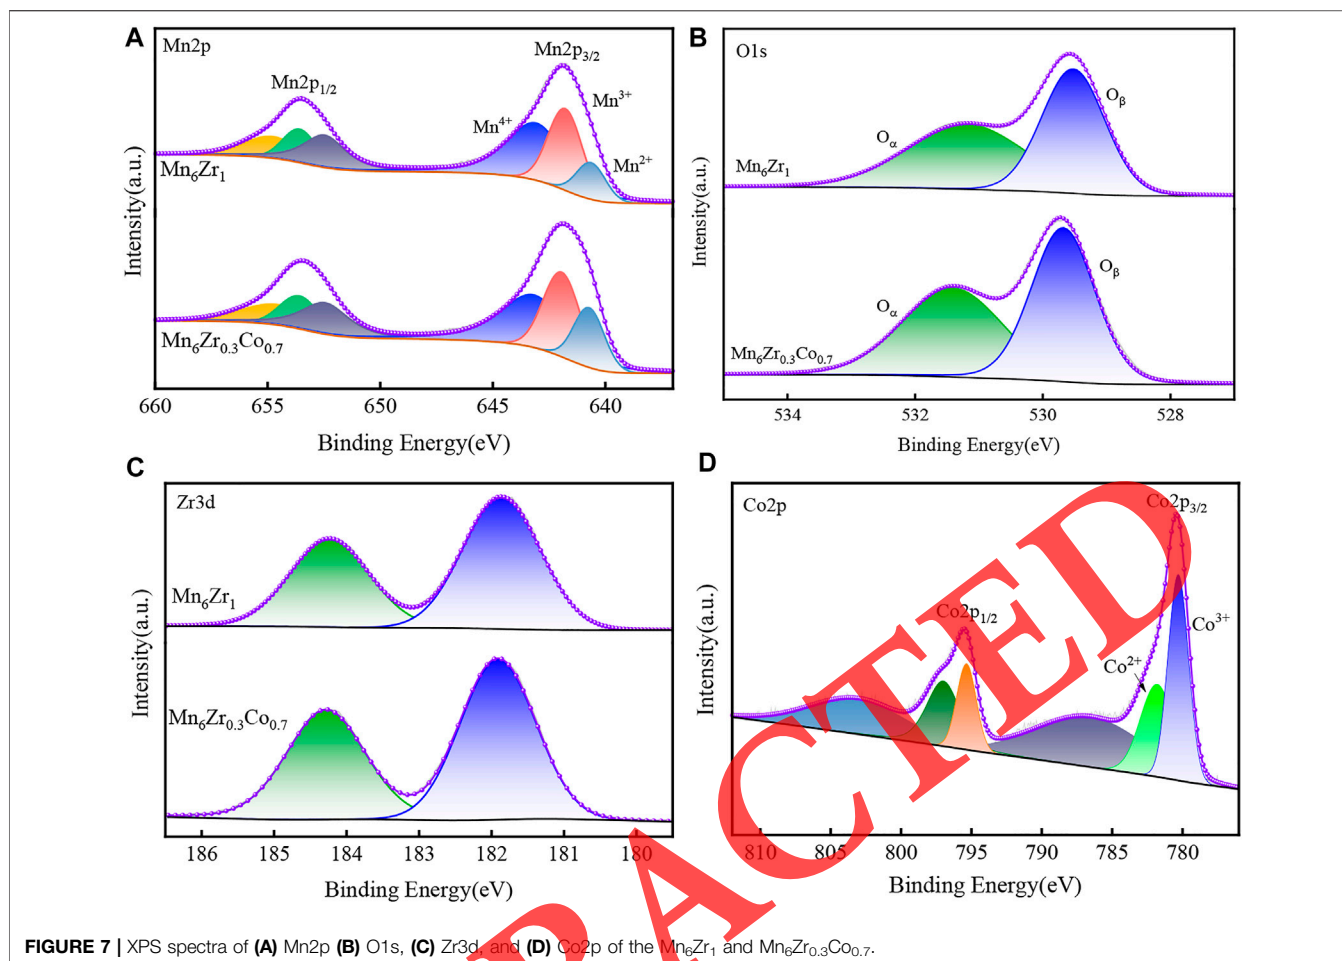


TABLE 2 | XPS test results of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts.

Catalysts	Mn 2p		O 1s	Co 2p	
	Mn ³⁺ /Mn	Mn ⁴⁺ /Mn	O _α /(O _α +O _β)	Co ³⁺ /Co	Co ³⁺ /Co ²⁺
Mn ₆ Zr ₁	34.32%	46.54%	47.94%	0	0
Mn ₆ Zr _{0.3} Co _{0.7}	31.04%	50.13%	48.16%	57%	133%

Mn₆Zr_{0.3}Co_{0.7} at liquid nitrogen temperature. The specific surface area, pore volume, and pore diameter of the three catalysts are shown in Table 1. In Figure 6A, the shapes of all isotherms can be regarded as type IV isotherms, which are characteristic of mesoporous materials (Jia et al., 2017). All the isotherms of the samples have lagged rings which can be attributed to type H3. When P/P₀ relative pressure is low, N₂ adsorption increases sharply, indicating the presence of narrow micropores in the catalyst (Huang et al., 2021). Figure 6B shows the pore size distribution of the catalyst. The results showed that the peak of the three catalysts at 2 nm belongs to micropore aggregation, and the wide peak at 3–7 nm belongs to mesoporous distribution. It shows that the samples are mainly mesoporous, supplemented by microporous. There are many intermediate holes in the catalyst, which are conducive to the removal of

NO_x, thus showing good catalytic activity. Table 1 shows that the specific surface area, pore volume, and pore size of the Mn₆Zr_{0.3}Co_{0.7} catalyst are increased to 156 m²/g, 0.29 cm³/g, and 3.7 nm, respectively, after the addition of cobalt. The results are consistent with SEM analysis of the Mn₆Zr_{0.3}Co_{0.7} catalyst. The increase of specific surface area is conducive to the dispersion of the active substance and the contact between the active site and the reactants, and the larger pore size can promote the rapid passage of the reactive gas, thus improving the NH₃-SCR activity of the catalyst (Zhai et al., 2021).

Analysis of Surface Element Composition

The surface elemental states of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts were characterized by XPS technology. The XPS analysis results are shown in Figure 7 and Table 2. The XPS

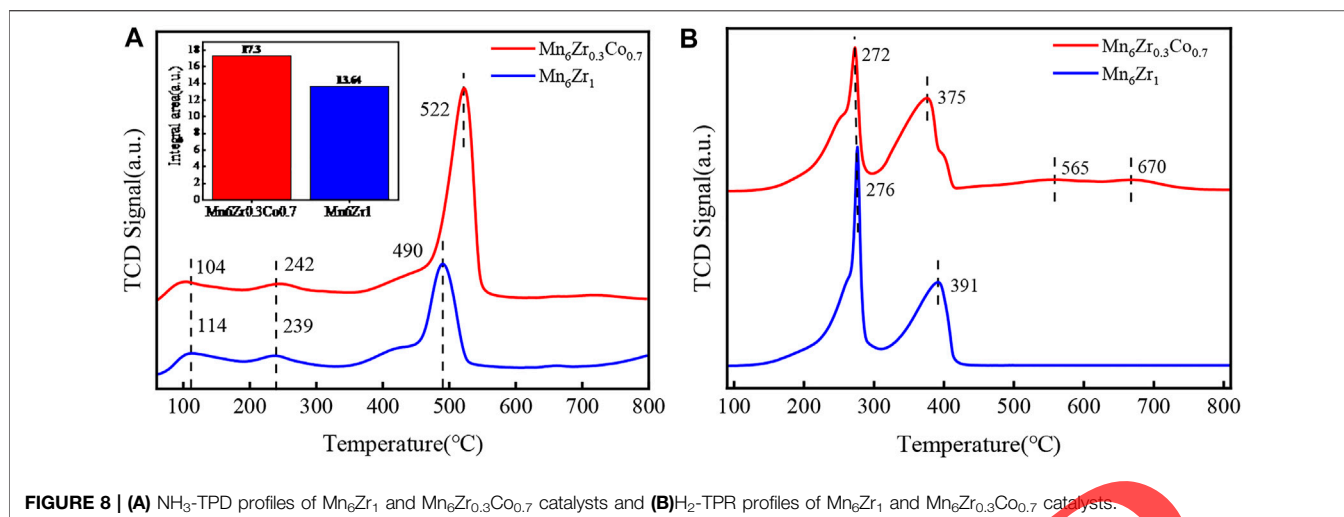


FIGURE 8 | (A) NH₃-TPD profiles of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts and **(B)** H₂-TPR profiles of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts.

spectra of Mn 2p showed two main peaks including Mn2p_{3/2} and Mn2p_{1/2}. Through peak fitting deconvolution, the three characteristic peaks of Mn⁴⁺, Mn³⁺, and Mn²⁺ in Mn2p_{3/2} on the Mn₆Zr₁ catalyst are 643.1, 641.7, and 640.6 eV, respectively. Mn2p_{3/2} is divided into the three characteristic peaks of 643.2, 641.9, and 640.7 eV on the Mn₆Zr_{0.3}Co_{0.7} catalyst corresponding to the binding energies of Mn⁴⁺, Mn³⁺, and Mn²⁺, respectively (Chen et al., 2020; Pan et al., 2020). As can be seen from Table 2, when the Co element is doped in the Mn₆Zr₁ catalyst, the Mn⁴⁺/Mn ratio in the Mn₆Zr_{0.3}Co_{0.7} catalyst is significantly higher than that obtained by Mn₆Zr₁. One possible reason is the interaction of cobalt and zirconium with manganese oxides. The ratio of Mn⁴⁺/Mn in the Mn₆Zr_{0.3}Co_{0.7} catalyst is larger than that of Mn³⁺/Mn, indicating that Mn⁴⁺ is dominant. In addition, the Mn⁴⁺ has the strongest catalytic activity in the NH₃-SCR reaction. This is one of the important reasons for the excellent activity of the Mn₆Zr_{0.3}Co_{0.7} catalyst (Chen et al., 2016b).


Figure 7B shows the XPS spectra of O1s of the two catalysts. The O1s peaks of both catalysts were composed of two fitting peaks of 529.5–529.8 eV and 531.1–531.4 eV, respectively. The former is attributed to lattice oxygen, denoted as O_β; The latter is attributed to adsorbed oxygen, denoted as O_α (Boningari et al., 2015). Table 2 shows that the O_α/(O_α+O_β) value of the Mn₆Zr_{0.3}Co_{0.7} catalyst is 48.16%, which is higher than that of Mn₆Zr₁ (47.97%). It can be seen that the adsorbed oxygen on the surface of Mn₆Zr₁ is more abundant. Since the mobility of chemisorbed oxygen is higher than that of lattice oxygen, chemisorbed oxygen is generally more active than lattice oxygen (Fan et al., 2018). Therefore, a higher O_α/(O_α+O_β) ratio is favorable for low-temperature NH₃-SCR reaction and capable of promoting the oxidation of NO to NO₂, thus accelerating the “Fast SCR” reaction (Zhang et al., 2018; Wu et al., 2021).

Figure 7C is the XPS spectrum of Zr3d. The binding energies of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts at Zr3d_{5/2} are 181.9 and 181.7 eV, respectively. The binding energy of Zr3d_{5/2} on pure ZrO₂ is 182.1 eV (Fang et al., 2018). The binding energy Mn₆Zr_{0.3}Co_{0.7} is significantly lower than that of the two other catalysts. A lower binding energy means more active elements, which will ultimately improve the catalytic reaction (Fang et al., 2017).

The XPS spectrum of Co2p is shown in Figure 7D. It can be seen that Co2p_{3/2} is fitted into three peaks. The peak at 780.3eV can be attributed to Co³⁺. The peak at 781.8 eV can be attributed to Co²⁺, and the other peak belongs to the satellite peak with a peak of 786.5 eV (Wang et al., 2019). According to the literature, Co³⁺ plays an important role in NH₃-SCR reaction. More Co³⁺ species on the catalyst surface, the better the redox performance of the catalyst (Meng et al., 2013). As can be seen from Table 2, the values of Co³⁺/Co and Co³⁺/Co²⁺ indicate that there are a large number of Co³⁺ species on the surface of the Mn₆Zr_{0.3}Co_{0.7} catalyst, and Co³⁺ occupies a dominant position, which well proves the reason for the excellent catalyst activity.

Temperature Programming Testing

The surface acidity of the catalyst is also very important in NH₃-SCR reactions. The surface acidity of the catalyst was investigated by using NH₃-TPD. As can be seen from Figure 8A, the desorption peaks of the two catalysts at around 100°C may be due to the physical adsorption of NH₃ at the weak acid site, and part of NH₄⁺ ions are adsorbed by the Brønsted acid site. The desorption peaks at 239 and 242°C are the chemical adsorption of NH₃ at the weak acid site (Liu et al., 2012; Jia et al., 2017). There is a desorption peak for catalyst Mn₆Zr₁ at 490°C and a desorption peak for catalyst Mn₆Zr_{0.3}Co_{0.7} at 522°C, both of which can be attributed to the adsorption of NH₃ at the Lewis acid site, but the former belongs to the medium acid site and the latter belongs to the strong acid site (Fang et al., 2013). As is known to all, the desorption peak area of the catalyst represents the amount of catalyst acid. By integrating the NH₃-TPD curve, the number of acid centers on the surface of Mn₆Zr_{0.3}Co_{0.7} and Mn₆Zr₁ catalysts can be estimated. It can be seen from the integral region of Figure 8A that the acid content of the Mn₆Zr_{0.3}Co_{0.7} catalyst is 17.3 μmol g⁻¹, which is significantly higher than that of the Mn₆Zr₁ catalyst 13.64 μmol g⁻¹. The results showed that the addition of cobalt not only enhanced the acidity of the catalyst surface but also increased the amount of acid, which was conducive to the adsorption of NH₃ and promoted the SCR reaction.

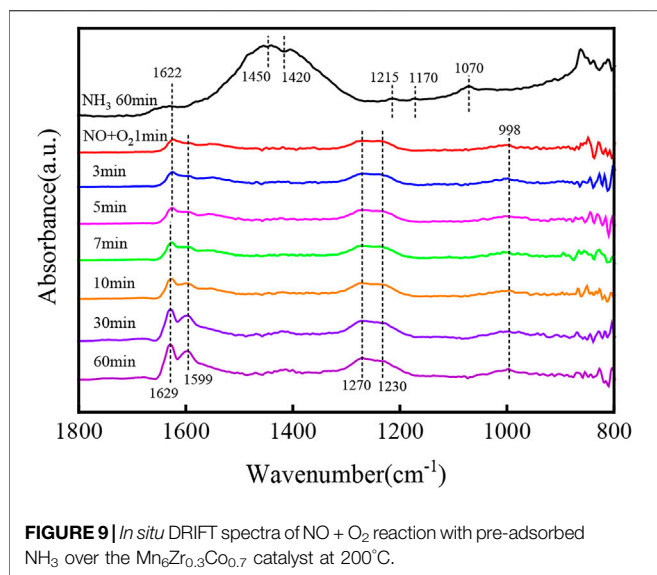

H₂-TPR was used to evaluate the redox performance of each catalyst and the interaction between the support and the active component. The redox capacity of the sample depended on the initial reduction temperature. In **Figure 8B**, both Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts have two reduction peaks. Studies had showed that all manganese-based catalysts follow MnO₂→Mn₃O₄→Mn₂O₃→MnO (Thirupathi and Smirniotis, 2011; France et al., 2017). Both catalysts show reduction peaks at 200–300°C and 300–500°C. The former can be attributed to the reduction of Mn⁴⁺→Mn³⁺ and Co³⁺→Co²⁺, while the latter can be attributed to the reduction of Mn³⁺→Mn²⁺ and Co²⁺→Co (Jiang and Song, 2013; Sun et al., 2018). The peak of the Mn₆Zr_{0.3}Co_{0.7} catalyst in the temperature range of 500–700°C can be attributed to the reduction of CoO (Lamonier et al., 2007). In addition, the reduction peak temperature of the Mn₆Zr_{0.3}Co_{0.7} catalyst is significantly lower than that of the Mn₆Zr₁ catalyst, which may be due to the formation of more surface oxygen vacancies in SCR reaction, which is conducive to the enhancement of oxygen fluidity or activation of reactants (Boningari et al., 2015). This indicates that the doping of cobalt enhances the redox capacity of the catalyst, which well-explains the reason why the Mn₆Zr_{0.3}Co_{0.7} catalyst has a good low-temperature denitration activity.

In situ DRIFT Analysis

The adsorption reaction of NH₃ and NO_x on the Mn₆Zr_{0.3}Co_{0.7} catalyst is the key to the SCR process. Therefore, *in situ* DRIFT spectra were carried out, and the results are shown in **Figure 9**. At 200°C, the Mn₆Zr_{0.3}Co_{0.7} sample was pre-adsorbed with NH₃ for 60min and then purged with N₂ for 30 min. After removing the physically adsorbed ammonia, the Mn₆Zr_{0.3}Co_{0.7} catalyst was exposed to the mixture of NO + O₂. The peaks at 1622 cm⁻¹ and 1170 cm⁻¹ were observed after NH₃ adsorption, which was due to the coordination state of NH₃ at the Lewis acid site on the catalyst surface (Han et al., 2019; Xiong et al., 2020). The characteristic peaks at 1450 cm⁻¹ and 1420 cm⁻¹ are attributed to the stretching


vibration of NH₄⁺ at the Brønsted acid sites (Zhang et al., 2021; Ge et al., 2022). Lewis and Brønsted acid sites coexist on the Mn₆Zr_{0.3}Co_{0.7} catalyst surface. In addition, a characteristic peak of coordination NH₃ appeared at 1215 cm⁻¹ (Han et al., 2019). The band at 1070 cm⁻¹ belongs to the active intermediate species NH₂. With the introduction of NO + O₂, the intensity of characteristic peaks of NH₄⁺, coordination NH₃, and amide (-NH₂) gradually decreased and disappeared rapidly. Bridging nitrates (1629 cm⁻¹, 1599 cm⁻¹, and 1230 cm⁻¹), bridged bidentate nitrate (1270 cm⁻¹), and nitrates (998 cm⁻¹) were formed (Han et al., 2019; Gong et al., 2020). All coordination NH₃, NH₄⁺, and -NH₂ are involved in the reaction. The removal of NO by NH₃-SCR on the Mn₆Zr_{0.3}Co_{0.7} catalyst follows L-H and E-R mechanisms according to the change of the characteristic peak of the *in situ* drift spectrum.

Kinetic Analysis

The SCR activity differences of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts were further investigated by kinetic experiments. According to the Arrhenius formula, the apparent activation energy E_a of NO_x conversion can be obtained by the slope of the lnk curve along with 1/T, as shown in **Figure 10**. It can be seen that the apparent activation energy E_a of Mn₆Zr₁ and Mn₆Zr_{0.3}Co_{0.7} catalysts is 22.53 kJ/mol and 5.41 kJ/mol, respectively. The results showed that zirconium doping significantly reduced the apparent activation energy of the catalyst. According to existing pieces of literature, the lower the activation energy of the catalyst, the higher the catalytic SCR activity (Wu et al., 2020).

ANALYSIS OF CATALYTIC MECHANISM

The Mn₆Zr_{0.3}Co_{0.7} catalyst prepared doping zirconium and cobalt into the MnO_x shows excellent denitrification ability and has a wide temperature window. The Mn₆Zr_{0.3}Co_{0.7} catalyst has a large specific surface area and abundant mesopores, which provides a convenient opportunity for gas adsorption and diffusion, thus improving the

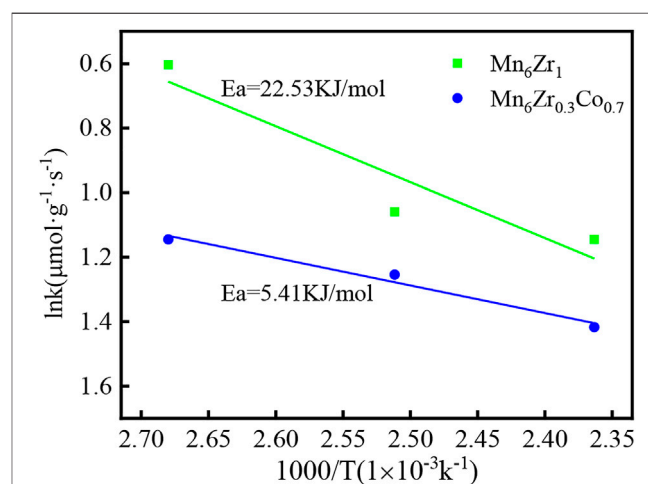

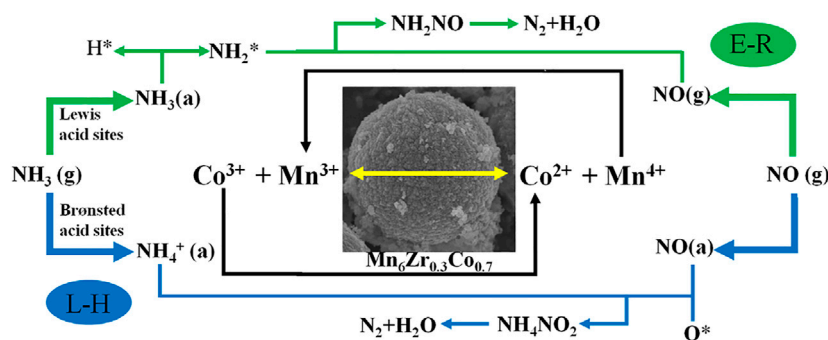


FIGURE 11 | Reaction mechanism of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst.

denitrification activity of the catalyst. Amorphous MnO_x , ZrO_2 , and CoO_x are formed on the surface of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst, which are the main active oxides on the surface of the catalyst, promoting SCR denitration of the catalyst. The elemental valence states on the surface of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst were characterized by XPS technology. The Mn^{4+} , O_α and Co^{3+} species on the surface of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst were increased. Mn^{4+} is considered to be one of the best low-temperature denitrification species. Adsorbed oxygen O_α has excellent oxygen mobility, which enables the rapid oxidation of NO to NO_2 , resulting in a Fast SCR reaction. Co^{3+} can promote the oxygen reduction performance of the catalyst. The surface acidity of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst was enhanced, which made it easier for the catalyst to adsorb NH_3 and activate or decompose NH_3 on its surface. At the same time, the reduction experiment of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst shows that the reduction temperature of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst decreases, which corresponds to the excellent denitrification activity of the catalyst at low temperature. In addition, the Lewis and Brønsted acid sites were found on the surface of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalysts.

The common NO removal process is divided into two steps: NO reacts with O_2 to form N_xO_y , which is further reduced to N_2 by adsorbed NH_3 . The former is closely related to reactive oxygen species, including lattice oxygen and adsorbed oxygen, while the latter participates in the cleavage of the N-H bond in NH_3 adsorbed on the Lewis acid site. Migration of H or NH_3 combines with a surface hydroxyl group to form NH_4^+ adsorbed on the Brønsted acid site. They can form intermediates NH_4NO_2 , NH_4NO_3 , and NH_2NO . Finally, these intermediates decompose into N_2 and H_2O . The $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst exhibits superior NH_3 -SCR denitrification capacity, which is mainly attributed to the excellent physicochemical properties of the catalyst. Combining the results with references (Jiang et al., 2021; Kang et al., 2021), the reaction path of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst can be described by E-R and L-H mechanisms. The whole reaction process is shown in Figure 11.

CONCLUSION

In this study, a series of $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalysts were prepared by doping of cobalt into the Mn_6Zr_1 catalyst. The catalytic

performance of the doped catalyst has been significantly improved in low-temperature denitrification performance, sulfur resistance, and water resistance. To be specific, the NO_x conversion of the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst is above 90% in the reaction temperature range of 100–275°C, and the best NO_x conversion is up to 99%. Under 200 ppm SO_2 , the NO_x conversion still remains above 90%. Under 5Vol% H_2O , the NO_x conversion basically remains at about 95%. According to the analysis of the characterization results, the $\text{Mn}_6\text{Zr}_{0.3}\text{Co}_{0.7}$ catalyst has a large specific surface area, pore size, pore volume, and strong redox performance, which are the main reasons for the excellent catalytic activity.

DATA AVAILABILITY STATEMENT

The raw data supporting the conclusions of this article will be made available by the authors, without undue reservation.

AUTHOR CONTRIBUTIONS

HL: conceptualization, methodology, validation, formal analysis, resources, investigation, writing—original draft, writing—review and editing, and visualization. SZ: conceptualization, methodology, formal analysis, resources, writing—original draft, and writing—review and editing. AZ: conceptualization, methodology, formal analysis, writing—original draft, writing—review and editing, and supervision. XZ: conceptualization, methodology, resources, supervision, project administration, and funding acquisition. ZS: conceptualization, methodology, formal analysis, resources, writing—original draft, and supervision. CY: conceptualization, methodology, formal analysis, resources. QZ: conceptualization, methodology, formal analysis, and resources.

FUNDING

The authors would like to acknowledge the National Natural Science Foundation of China for funding with the grant of U1504217, 51306046, and 51676064.

REFERENCES

- Ali, S., Chen, L., Yuan, F., Li, R., Zhang, T., Bakhtiar, S. u. H., et al. (2017). Synergistic Effect between Copper and Cerium on the Performance of Cu X -Ce 0.5-x -Zr 0.5 (X = 0.1-0.5) Oxides Catalysts for Selective Catalytic Reduction of NO with Ammonia. *Appl. Catal. B Environ.* 210, 223–234. doi:10.1016/j.apcatb.2017.03.065
- Azalim, S., Franco, M., Brahmī, R., Giraudon, J.-M., and Lamonier, J.-F. (2011). Removal of Oxygenated Volatile Organic Compounds by Catalytic Oxidation over Zr-Ce-Mn Catalysts. *J. Hazard. Mater.* 188, 422–427. doi:10.1016/j.jhazmat.2011.01.135
- Boningari, T., Ettireddy, P. R., Somogyvari, A., Liu, Y., Vorontsov, A., McDonald, C. A., et al. (2015). Influence of Elevated Surface Texture Hydrated Titania on Ce-Doped Mn/TiO₂ Catalysts for the Low-Temperature SCR of NO under Oxygen-Rich Conditions. *J. Catal.* 325, 145–155. doi:10.1016/j.jcat.2015.03.002
- Chen, J., Fu, P., Lv, D., Chen, Y., Fan, M., Wu, J., et al. (2021). Unusual Positive Effect of SO₂ on Mn-Ce Mixed-Oxide Catalyst for the SCR Reaction of NO_x with NH₃. *Chem. Eng. J.* 407, 127071–127110. doi:10.1016/j.cej.2020.127071
- Chen, Q.-l., Guo, R.-t., Wang, Q.-s., Pan, W.-g., Wang, W.-h., Yang, N.-z., et al. (2016). The Catalytic Performance of Mn/TiWO Catalyst for Selective Catalytic Reduction of NO with NH₃. *Fuel* 181, 852–858. doi:10.1016/j.fuel.2016.05.045
- Chen, Q.-l., Guo, R.-t., Wang, Q.-s., Pan, W.-g., Wang, W.-h., Yang, N.-z., et al. (2016). The Catalytic Performance of Mn/TiWO Catalyst for Selective Catalytic Reduction of NO with NH₃. *Fuel* 181, 852–858. doi:10.1016/j.fuel.2016.05.045
- Chen, S., Vasiliades, M. A., Yan, Q., Yang, G., Du, X., Zhang, C., et al. (2020). Remarkable N₂-Selectivity Enhancement of Practical NH₃-SCR over Co_{0.5}Mn₁Fe_{0.25}Al_{0.75}Ox-LDO: The Role of Co Investigated by Transient Kinetic and DFT Mechanistic Studies. *Appl. Catal. B Environ.* 277, 119186–119219. doi:10.1016/j.apcatb.2020.119186
- Fan, Z., Shi, J.-W., Gao, C., Gao, G., Wang, B., Wang, Y., et al. (2018). Gd-modified MnO_x for the Selective Catalytic Reduction of NO by NH₃: The Promoting Effect of Gd on the Catalytic Performance and Sulfur Resistance. *Chem. Eng. J.* 348, 820–830. doi:10.1016/j.cej.2018.05.038
- Fang, C., Zhang, D., Cai, S., Zhang, L., Huang, L., Li, H., et al. (2013). Low-temperature Selective Catalytic Reduction of NO with NH₃ over Nanoflaky MnO_x on Carbon Nanotubes *In Situ* Prepared via a Chemical Bath Deposition Route. *Nanoscale* 5, 9199–9207. doi:10.1039/c3nr02631k
- Fang, N., Guo, J., Shu, S., Luo, H., Chu, Y., and Li, J. (2017). Enhancement of Low-Temperature Activity and Sulfur Resistance of Fe_{0.3}Mn_{0.5}Zr_{0.2} Catalyst for NO Removal by NH₃-SCR. *Chem. Eng. J.* 325, 114–123. doi:10.1016/j.cej.2017.05.053
- Fang, N., Guo, J., Shu, S., Luo, H., Li, J., and Chu, Y. (2018). Effect of Calcination Temperature on Low-Temperature NH₃-SCR Activity and the Resistance of SO₂ with or without H₂O over Fe-Mn-Zr Catalyst. *J. Taiwan Inst. Chem. Eng.* 93, 277–288. doi:10.1016/j.tic.2018.07.027
- France, L. J., Yang, Q., Li, W., Chen, Z., Guang, J., Guo, D., et al. (2017). Ceria Modified FeMnO_x-Enhanced Performance and Sulphur Resistance for Low-Temperature SCR of NO_x. *Appl. Catal. B Environ.* 206, 203–215. doi:10.1016/j.apcatb.2017.01.019
- Gao, F., Tang, X., Yi, H., Zhao, S., Wang, J., Shi, Y., et al. (2018). Novel Co- or Ni-Mn Binary Oxide Catalysts with Hydroxyl Groups for NH₃-SCR of NO_x at Low Temperature. *Appl. Surf. Sci.* 443, 103–113. doi:10.1016/j.apsusc.2018.02.151
- Gao, F., Walter, E. D., Kollar, M., Wang, Y., Szanyi, J., and Peden, C. H. F. (2014). Understanding Ammonia Selective Catalytic Reduction Kinetics over Cu/SSZ-13 from Motion of the Cu Ions. *J. Catal.* 319, 1–14. doi:10.1016/j.jcat.2014.08.010
- Ge, Z., Shen, Y., and Gu, S. (2022). High-temperature Selective Catalytic Reduction of NO with NH₃: Optimization of ZrO₂ and WO₃ Complex Oxides. *Fuel* 310, 122261–122268. doi:10.1016/j.fuel.2021.122261
- Gong, P., Xie, J., Fang, D., He, F., Li, F., and Qi, K. (2020). Enhancement of the NH₃-SCR Property of Ce-Zr-Ti by Surface and Structure Modification with P. *Appl. Surf. Sci.* 505, 144641–144649. doi:10.1016/j.apsusc.2019.144641
- Guo, M., Liu, Q., Liu, C., Wang, X., Bi, Y., Fan, B., et al. (2021). Rational Design of Novel CrZrO Catalysts for Efficient Low Temperature SCR of NO. *Chem. Eng. J.* 413, 127554. doi:10.1016/j.cej.2020.127554
- Han, S., Cheng, J., Ye, Q., Cheng, S., Kang, T., and Dai, H. (2019). Ce Doping to Cu-SAPO-18: Enhanced Catalytic Performance for the NH₃-SCR of NO in Simulated Diesel Exhaust. *Microporous Mesoporous Mater.* 276, 133–146. doi:10.1016/j.micromeso.2018.09.027
- Hu, G., Yang, J., Tian, Y., Kong, B., Liu, Q., Ren, S., et al. (2018). Effect of Ce Doping on the Resistance of Na over V₂O₅-WO₃/TiO₂ SCR Catalysts. *Mater. Res. Bull.* 104, 112–118. doi:10.1016/j.materresbull.2018.04.009
- Hu, H., Cai, S., Li, H., Huang, L., Shi, L., and Zhang, D. (2015). *In Situ* DRIFTS Investigation of the Low-Temperature Reaction Mechanism over Mn-Doped Co₃O₄ for the Selective Catalytic Reduction of NO_x with NH₃. *J. Phys. Chem. C* 119, 22924–22933. doi:10.1021/acs.jpcc.5b06057
- Hu, X., Shi, Q., Zhang, H., Wang, P., Zhan, S., and Li, Y. (2017). NH₃-SCR Performance Improvement over Mo Modified Mo(x)-MnO_x Nanorods at Low Temperatures. *Catal. Today* 297, 17–26. doi:10.1016/j.cattod.2017.06.015
- Huang, X., Dong, F., Zhang, G., Guo, Y., and Tang, Z. (2021). A Strategy for Constructing Highly Efficient Yolk-Shell Ce@Mn@TiO_x Catalyst with Dual Active Sites for Low-Temperature Selective Catalytic Reduction of NO with NH₃. *Chem. Eng. J.* 419, 129572–129613. doi:10.1016/j.cej.2021.129572
- Jia, B., Guo, J., Luo, H., Shu, S., Fang, N., and Li, J. (2018). Study of NO Removal and Resistance to SO₂ and H₂O of MnO/TiO₂, MnO/ZrO₂ and MnO/ZrO₂-TiO₂. *Appl. Catal. A General* 553, 82–90. doi:10.1016/j.apcata.2017.12.016
- Jia, B., Guo, J., Shu, S., Fang, N., Li, J., and Chu, Y. (2017). Effects of Different Zr/Ti Ratios on NH₃-SCR over MnO/Zr-Ti-O₂: Characterization and Reaction Mechanism. *Mol. Catal.* 443, 25–37. doi:10.1016/j.mcat.2017.09.019
- Jiang, H., Guan, B., Peng, X., Zhan, R., Lin, H., and Huang, Z. (2020). Influence of Synthesis Method on Catalytic Properties and Hydrothermal Stability of Cu/SSZ-13 for NH₃-SCR Reaction. *Chem. Eng. J.* 379, 122358–122415. doi:10.1016/j.cej.2019.122358
- Jiang, S. J., and Song, S. Q. (2013). Enhancing the Performance of Co₃O₄/CNTs for the Catalytic Combustion of Toluene by Tuning the Surface Structures of CNTs. *Appl. Catal. B: Environ.* 140, 1–8. doi:10.1016/j.apcatb.2013.03.040
- Jiang, Y., Liu, T., Li, C., Yang, Z., Lin, R., Wang, X., et al. (2021). Deactivation of CeO₂-TiO₂ Catalyst by K₂SO₄ for NH₃-SCR: An Experimental and DFT Study. *Appl. Surf. Sci.* 547, 149196–149210. doi:10.1016/j.apsusc.2021.149196
- Jin, Q., Shen, Y., Mei, C., Zhang, Y., and Zeng, Y. (2022). Catalytic Removal of NO and Dioxins over W-Zr-Ox/Ti-Ce-Mn-Ox from Flue Gas: Performance and Mechanism Study. *Catal. Today* 388–389, 372–382. doi:10.1016/j.cattod.2020.05.061
- Kang, K., Yao, X., Huang, Y., Cao, J., Rong, J., Zhao, W., et al. (2021). Insights into the Co-doping Effect of Fe³⁺ and Zr⁴⁺ on the Anti-K Performance of CeTiO_x Catalyst for NH₃-SCR Reaction. *J. Hazard. Mater.* 416, 125821–125913. doi:10.1016/j.jhazmat.2021.125821
- Kantcheva, M., Cayirtepe, I., Naydenov, A., and Ivanov, G. (2011). FT-IR Spectroscopic Investigation of the Effect of SO₂ on the SCR of NO_x with Propene over ZrO₂-Nb₂O₅ Catalyst. *Catal. Today* 176, 437–440. doi:10.1016/j.cattod.2010.10.072
- Kwon, D. W., Park, K. H., and Hong, S. C. (2016). Enhancement of SCR Activity and SO₂ Resistance on VO_x/TiO₂ Catalyst by Addition of Molybdenum. *Chem. Eng. J.* 284, 315–324. doi:10.1016/j.cej.2015.08.152
- Lamonier, J.-F., Boutoundou, A.-B., Gennequin, C., Pérez-Zurita, M. J., Siffert, S., and Aboukais, A. (2007). Catalytic Removal of Toluene in Air over Co-mn-al Nano-Oxides Synthesized by Hydrotalcite Route. *Catal. Lett.* 118, 165–172. doi:10.1007/s10562-007-9196-4
- Liu, Y., Gu, T., Weng, X., Wang, Y., Wu, Z., and Wang, H. (2012). DRIFT Studies on the Selectivity Promotion Mechanism of Ca-Modified Ce-Mn/TiO₂ Catalysts for Low-Temperature NO Reduction with NH₃. *J. Phys. Chem. C* 116, 16582–16592. doi:10.1021/jp304390e
- Meng, B., Zhao, Z., Wang, X., Liang, J., and Qiu, J. (2013). Selective Catalytic Reduction of Nitrogen Oxides by Ammonia over Co₃O₄ Nanocrystals with Different Shapes. *Appl. Catal. B Environ.* 129, 491–500. doi:10.1016/j.apcatb.2012.09.040
- Pan, Y., Shen, B., Liu, L., Yao, Y., Gao, H., Liang, C., et al. (2020). Develop High Efficient of NH₃-SCR Catalysts with Wide Temperature Range by Ball-Milled Method. *Fuel* 282, 118834–118914. doi:10.1016/j.fuel.2020.118834
- Shi, A., Wang, X., Yu, T., and Shen, M. (2011). The Effect of Zirconia Additive on the Activity and Structure Stability of V₂O₅/WO₃-TiO₂ Ammonia SCR Catalysts. *Appl. Catal. B Environ.* 106, 359–369. doi:10.1016/j.apcatb.2011.05.040

- Sun, X., Guo, R.-t., Liu, J., Fu, Z.-g., Liu, S.-w., Pan, W.-g., et al. (2018). The Enhanced SCR Performance of Mn/TiO₂ Catalyst by Mo Modification: Identification of the Promotion Mechanism. *Int. J. Hydrogen Energy* 43, 16038–16048. doi:10.1016/j.ijhydene.2018.07.057
- Tang, X., Hao, J., Xu, W., and Li, J. (2007). Low Temperature Selective Catalytic Reduction of NO with NH₃ over Amorphous MnO Catalysts Prepared by Three Methods. *Catal. Commun.* 8, 329–334. doi:10.1016/j.catcom.2006.06.025
- Tang, X., Wang, C., Gao, F., Ma, Y., Yi, H., Zhao, S., et al. (2020). Effect of Hierarchical Element Doping on the Low-Temperature Activity of Manganese-Based Catalysts for NH₃-SCR. *J. Environ. Chem. Eng.* 8, 104399–104410. doi:10.1016/j.jece.2020.104399
- Thirupathi, B., and Smirniotis, P. G. (2011). Co-doping a Metal (Cr, Fe, Co, Ni, Cu, Zn, Ce, and Zr) on Mn/TiO₂ Catalyst and its Effect on the Selective Reduction of NO with NH₃ at Low-Temperatures. *Appl. Catal. B Environ.* 110, 195–206. doi:10.1016/j.apcatb.2011.09.001
- Wang, R., Hao, Z., Li, Y., Liu, G., Zhang, H., Wang, H., et al. (2019). Relationship between Structure and Performance of a Novel Highly Dispersed MnOx on Co-al Layered Double Oxide for Low Temperature NH₃-SCR. *Appl. Catal. B Environ.* 258, 117983–117989. doi:10.1016/j.apcatb.2019.117983
- Wang, X., Wu, S., Zou, W., Yu, S., Gui, K., and Dong, L. (2016). Fe-Mn/Al₂O₃ Catalysts for Low Temperature Selective Catalytic Reduction of NO with NH₃. *Chin. J. Catal.* 37, 1314–1323. doi:10.1016/S1872-2067(15)61115-9
- Wu, R., Li, L., Zhang, N., He, J., Song, L., Zhang, G., et al. (2021). Enhancement of Low-Temperature NH₃-SCR Catalytic Activity and H₂O & SO₂ Resistance over Commercial V₂O₅-MoO₃/TiO₂ Catalyst by High Shear-Induced Doping of Expanded Graphite. *Catal. Today* 376, 302–310. doi:10.1016/j.cattod.2020.04.051
- Wu, X., Meng, H., Du, Y., Liu, J., Hou, B., and Xie, X. (2020). Insight into Cu₂O/CuO Collaboration in the Selective Catalytic Reduction of NO with NH₃: Enhanced Activity and Synergistic Mechanism. *J. Catal.* 384, 72–87. doi:10.1016/j.jcat.2020.01.025
- Xiong, S., Peng, Y., Wang, D., Huang, N., Zhang, Q., Yang, S., et al. (2020). The Role of the Cu Dopant on a Mn₃O₄ Spinel SCR Catalyst: Improvement of Low-Temperature Activity and Sulfur Resistance. *Chem. Eng. J.* 387, 124090–124112. doi:10.1016/j.cej.2020.124090
- Zhai, G., Han, Z., Wu, X., Du, H., Gao, Y., Yang, S., et al. (2021). Pr-modified MnO Catalysts for Selective Reduction of NO with NH₃ at Low Temperature. *J. Taiwan Inst. Chem. Eng.* 125, 132–140. doi:10.1016/j.jtice.2021.06.008
- Zhang, K., Yu, F., Zhu, M., Dan, J., Wang, X., Zhang, J., et al. (2018). Enhanced Low Temperature NO Reduction Performance via MnOx-Fe₂O₃/Vermiculite Monolithic Honeycomb Catalysts. *Catalysts* 8, 100–115. doi:10.3390/catal8030100
- Zhang, L., Shi, L., Huang, L., Zhang, J., Gao, R., and Zhang, D. (2014). Rational Design of High-Performance DeNO_x Catalysts Based on Mn_xCo_{3-x}O₄ Nanocages Derived from Metal-Organic Frameworks. *ACS Catal.* 4, 1753–1763. doi:10.1021/cs401185c
- Zhang, Y., Zheng, Y., Wang, X., and Lu, X. (2015). Preparation of Mn-FeOx/CNTs Catalysts by Redox Co-precipitation and Application in Low-Temperature NO Reduction with NH₃. *Catal. Commun.* 62, 57–61. doi:10.1016/j.catcom.2014.12.023
- Zhang, Z., Li, R., Wang, M., Li, Y., Tong, Y., Yang, P., et al. (2021). Two Steps Synthesis of CeTiOx Oxides Nanotube Catalyst: Enhanced Activity, Resistance of SO₂ and H₂O for Low Temperature NH₃-SCR of NO_x. *Appl. Catal. B Environ.* 282, 119542–119612. doi:10.1016/j.apcatb.2020.119542
- Zhou, X., Dan, J., Zhang, J., Yang, S., Shi, L., Wang, J., et al. (2019). Two-dimensional MnAl Mixed-Metal Oxide Nanosheets Prepared via a High-Shear-Mixer-Facilitated Coprecipitation Method for Enhanced Selective Catalytic Reduction of NO with NH₃. *Chem. Eng. Process. - Process Intensif.* 145, 107664–107669. doi:10.1016/j.cep.2019.107664

Conflict of Interest: The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Publisher's Note: All claims expressed in this article are solely those of the authors and do not necessarily represent those of their affiliated organizations, or those of the publisher, the editors, and the reviewers. Any product that may be evaluated in this article, or claim that may be made by its manufacturer, is not guaranteed or endorsed by the publisher.

Copyright © 2022 Li, Zhang, Zhang, Sun, Yang and Zhu. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.

RETRACTED