



Fabrication of VO₂-Dispersed Glass in B₂O₃-P₂O₅-V₂O₅ System and Its Thermal Property

Kei Muramoto¹, Yoshihiro Takahashi^{1*}, Nobuaki Terakado¹, Yoshiki Yamazaki², Shigeru Suzuki² and Takumi Fujiwara^{1*}

¹ Department of Applied Physics, Graduate School of Engineering, Tohoku University, Sendai, Japan, ² Institute of Multidisciplinary Research for Advanced Materials, Tohoku University, Sendai, Japan

OPEN ACCESS

Edited by:

Ashutosh Goel,
Rutgers, The State University of New
Jersey, United States

Reviewed by:

Guglielmo Macrelli,
Independent Researcher, Este, Italy
Nadja Lönnroth,
Huawei Technologies Oy (Finland)
Co. Ltd, Finland

*Correspondence:

Yoshihiro Takahashi
takahashi@laser.apph.tohoku.ac.jp
Takumi Fujiwara
fujiwara@laser.apph.tohoku.ac.jp

Specialty section:

This article was submitted to
Glass Science,
a section of the journal
Frontiers in Materials

Received: 15 October 2019

Accepted: 07 January 2020

Published: 18 February 2020

Citation:

Muramoto K, Takahashi Y,
Terakado N, Yamazaki Y, Suzuki S and
Fujiwara T (2020) Fabrication of
VO₂-Dispersed Glass in
B₂O₃-P₂O₅-V₂O₅ System and Its
Thermal Property. *Front. Mater.* 7:5.
doi: 10.3389/fmats.2020.00005

Phase change material (PCM), which enables heat storage based on phase transition, plays an important role for efficient energy utilization. This paper briefly describes our recent study about all-solid PCM by combination of vanadium dioxide (VO₂) with latent heat storage capacity and multicomponent glass, i.e., VO₂-dispersed glass. A B₂O₃-P₂O₅-V₂O₅ glass system is used as a matrix for the VO₂-dispersed glass. An attempt to describe its latent heat storage function is given. Endothermic behavior due to structural phase transition of the VO₂ crystals was observed in the VO₂-dispersed sample, and the transition enthalpy corresponding to latent heat storage capacity was estimated to be $\Delta H \sim 9.5$ J/g. The value of the studied sample was larger than the value of dispersed glass in the BaO-TeO₂-V₂O₅ system that was previously reported. Potential for PCM was considered in the studied sample.

Keywords: glass, vanadium dioxide, latent heat storage, vanadate, thermal property

INTRODUCTION

Heat storage technology is essential for efficient energy utilization and sustainable development because the technology can appropriately balance the supply and demand amounts of thermal energy for different times and/or spaces (Nomura et al., 2015a). For heat storage, materials able to release the absorbed/conserved energy, i.e., heat storage materials, play a crucial role. Particularly, the latent heat storage is based on the capture or release of energy when a material undergoes a phase change between solid and liquid state, and heat storage materials based on the phase transition are referred to as phase change materials (PCMs) (Hasnain, 1998; Farid et al., 2004; Jacob and Bruno, 2015). For example, ice, paraffin, fatty acids, and inorganic hydrates are frequently utilized as PCMs. However, since the heat storage mechanism of these PCMs involves a solid-liquid phase transition, it is imperative to ensure that the PCM inside the container is maintained in the liquid state. Moreover, damage to the container because of the large volume change occurring during the phase transition and leaking out of the liquid are inevitable. In order to prevent these issues coming from the presence of the liquid state, it is of particular interest to develop new PCMs (Nomura et al., 2015b; Tokoro et al., 2015).

A strongly correlated electron system, vanadium dioxide (VO₂), has gained much interest as a PCM. A reversible solid-solid phase transition occurs at 68°C, accompanying an exothermic or endothermic reaction, and the latent heat of VO₂ is comparable to that of the typical PCMs (Niitaka et al., 2010; Wu et al., 2011). Although VO₂ is commercially available as a powder, if we use the VO₂ powder as PCM, it is mandatory to use a container matrix. Thus, VO₂ exhibits some disadvantages that impede large-scale PCM applications.

Glass exhibits immense advantages from the viewpoint of materials science, e.g., large-scale or mass production, flexibility, and formability (Sakamoto and Yamamoto, 2010). Recently, the authors' group has proposed a new PCM, i.e., VO₂-dispersed glass, where the VO₂ powders embedded in the glass matrix serve as a durable container-free PCM (Muramoto et al., 2018). 30BaO-10TeO₂-60V₂O₅ (in mol%) glass was selected as the matrix on the basis of thermal and water-immersion tests. It was suggested that the Te-O polyhedral units contributed to a three-dimensional network structure of the glass (Ahamad et al., 2012), resulting in its high water resistivity. On the other hand, the deposit amount of Te element is relatively small, being comparable to that of noble metals, and additionally Te, and its related compounds are toxic. Another candidate in the vanadate system, B₂O₃-P₂O₅-V₂O₅ glass, was also considered, even though it possessed low water resistivity. Nevertheless, B₂O₃-P₂O₅-V₂O₅ glass consists of much more common and less-toxic substances, i.e., B₂O₃ and P₂O₅, and these oxides possess a considerably low melting temperature compared to that of a typical glass-former, SiO₂. These lead us to consider that VO₂ powder can be incorporated into a B₂O₃-P₂O₅-V₂O₅ glass without any degradation. Therefore, in this study, we have fabricated VO₂-dispersed glasses by an incorporation technique and then examined the endothermic behavior based on the phase transition of VO₂ crystals.

EXPERIMENT

In this study, the matrix glass with a composition of 15B₂O₃-10P₂O₅-75V₂O₅ (in mol%) was prepared by a conventional melt-quenching technique using an alumina crucible with a lid. Commercial reagent-grade powders of B₂O₃, (NH₄)₂HPO₄, and V₂O₅ were used as raw materials. The mixture of the raw materials was melted at 800°C for 60 min under air. The melt was poured onto a steel plate heated at ~200°C, followed by


pressing using another steel plate to obtain the as-quenched sample. The sample was confirmed to be in amorphous state as evidenced by X-ray diffraction (XRD) analysis (Cu-K α radiation). Subsequently, to fabricate the VO₂-dispersed glass, the incorporation method reported by Komatsu et al. (1995) was employed in the study: A powdered matrix glass and VO₂ powder (purity: 99.9%; Kojundo Chemical Laboratory Co., Ltd.) were mixed using an alumina mortar. Second, the mixture was added into an alumina crucible and melted at 1,200°C for 15 min under air. The quenching process was similar to that utilized during the preparation of the matrix glass, finally furnishing VO₂-dispersed glass.

The state of crystal phase in the dispersed sample was confirmed by XRD analysis and scanning electron microscope (SEM). Prior to XRD measurement, the dispersed samples were powdered by the use of an alumina mortar. The thermal properties of the matrix glass and VO₂-dispersed samples and glass-transition (T_g), crystallization-onset (T_x), and crystallization-peak temperatures (T_p), were examined by differential thermal analysis (DTA; heating rate of 10 K/min, Rigaku Corporation, Thermoplus TG8120). The transition enthalpy (ΔH), which corresponds to the amount of the stored latent heat, of the VO₂-dispersed sample was evaluated by differential scanning calorimetry (DSC; heating rate of 1 K/min, Seiko Instruments Inc., DSC6220). The specific heat, C_p [$= (\frac{\partial H}{\partial T})_p$], was measured as a function of temperature (T), and ΔH was estimated on the basis of the thermodynamic relation, i.e., $H = \int C_p dT$. The sample state used in the measurement was the bulk form with a weight of ca. 10 mg.

RESULTS

Characterizations of the VO₂-Dispersed Glass

Prior to fabrication of the VO₂-dispersed sample, the 15B₂O₃-10P₂O₅-75V₂O₅ glass (matrix) was examined. The XRD

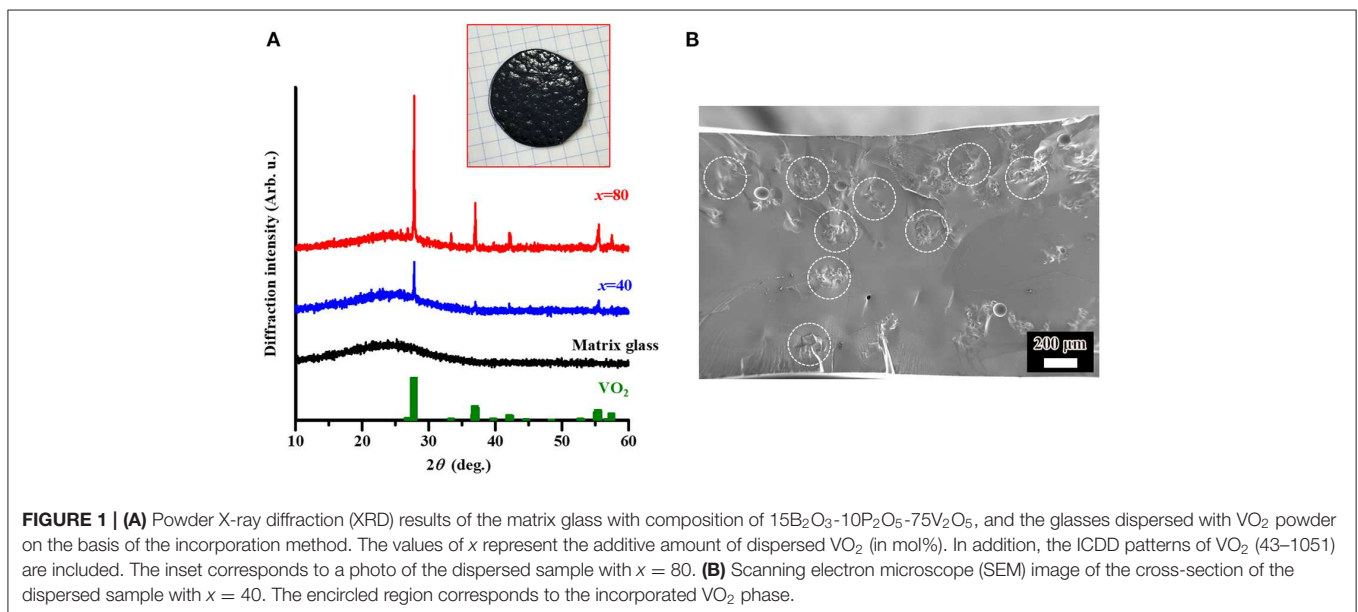

measurement of the as-quenched sample indicated a halo pattern without any sharp diffraction peaks, which is a characteristic of the amorphous phase (cf. **Figure 1**). We have already obtained the DTA curve of 15B₂O₃-10P₂O₅-75V₂O₅ glass (Muramoto et al., 2018), and the parameters could be estimated on the basis of the previous DTA results as $T_g = 225^\circ\text{C}$, $T_x = 266^\circ\text{C}$, and $T_p = 279^\circ\text{C}$. The values of T_g and T_p were almost identical to the values by Choi et al. (Choi and Ryu, 2015).

The VO₂-dispersed glasses with different additive amounts (x ; mol%) of VO₂ phase, i.e., 15B₂O₃-10P₂O₅-75V₂O₅: x VO₂ composites with $x = 40$ and 80 , were studied by XRD analysis. As a result, the crystalline diffraction peaks corresponding to VO₂ phase could be observed in combination with the amorphous halo patterns due to matrix glass (**Figure 1A**), and the intensity of diffraction peaks increased with x . In addition, SEM observation was conducted in the sample with $x = 40$ as a representative in order to check the dispersion state in the matrix glass. As a result, we can see the inclusions with a size of ca. 100 μm , i.e., the presence of aggregation of VO₂ particles (**Figure 1B**). The XRD and SEM results suggest that the VO₂ phase is stably incorporated in the matrix glass. A

possible explanation of the stable incorporation could be given by an abundance of vanadium around the incorporated VO₂ phase, i.e., saturation of vanadium in the matrix glass, resulting in the suppression of vanadium migration/diffusion from the VO₂ (Muramoto et al., 2018). Furthermore, the melting point of VO₂ ($\sim 1,970^\circ\text{C}$) is much higher than the processing temperature for incorporation ($1,200^\circ\text{C}$). This probably contributes to the stable incorporation as well.

As the result of DTA, the dispersed samples exhibited similar DTA curves to the matrix glass, i.e., endothermic region ($224\text{--}229^\circ\text{C}$) and sharp exothermic peaks ($280\text{--}290^\circ\text{C}$), which correspond to the T_g and T_p , respectively (**Figure 2**). We have found that the matrix glass crystallizes the V₂O₅ phase by means of thermal treatment at the T_p (Muramoto et al., 2018). In this study, crystallization of the V₂O₅ phase was also confirmed in the dispersed glasses heat-treated at the T_p for 1 h by means of the XRD measurement. Furthermore, we should mention that clear endothermic peaks are observed in the temperature range of $\sim 60\text{--}80^\circ\text{C}$ (onset temperature: $63\text{--}66^\circ\text{C}$), which is much lower than the T_g . Since their peaks tend to be large as the increase in x , it is reasonable to consider that the endothermic peaks originate from the phase transition of the dispersed VO₂ phase because of the $T_c \sim 68^\circ\text{C}$. Thus, we have concluded that VO₂-dispersed glass was successfully fabricated in the B₂O₃-P₂O₅-V₂O₅ system. This also leads us to expect that heat storage based on the solid-state phase transition of VO₂ is possible in the dispersed glass sample. Meanwhile, the endothermic peak of the sample with $x = 40$ was relatively smaller than the peak expected from the sample with $x = 80$, in which the amount of the VO₂ phase is double. As a possible explanation, the smallness of the endothermic peak is supposed

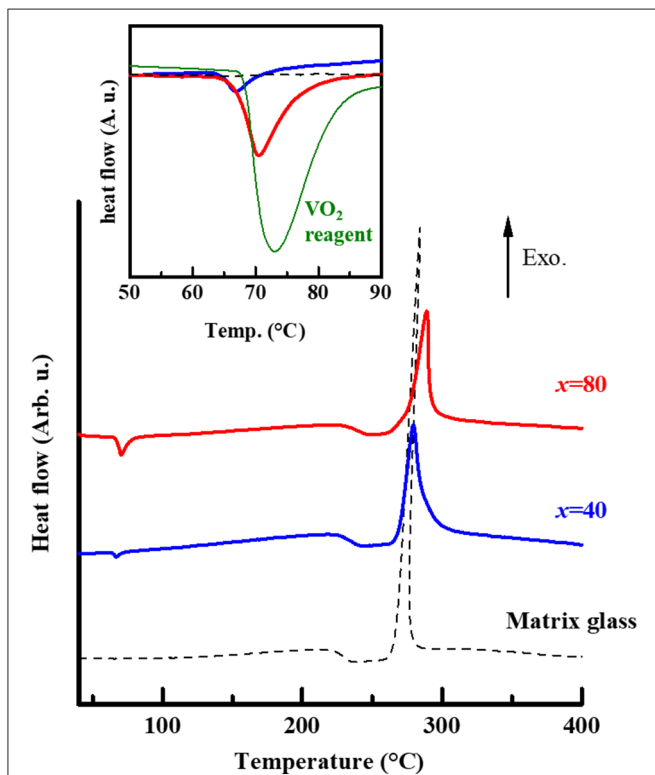


FIGURE 2 | Differential thermal analysis (DTA) results of the dispersed samples, 15B₂O₃-10P₂O₅-75V₂O₅: x ($x = 40$ and 80 ; the studied samples are bulk form), together with the result of matrix glass referred from the paper (Muramoto et al., 2018). The inset shows the DTA curves in a low-temperature region, in which an endothermic reaction was observed in the heating process. The endothermic peaks with onset temperature are around the vicinity of $T_c \sim 68^\circ\text{C}$, indicating the structural phase transition of the dispersed VO₂ phase. The DTA result in the VO₂ reagent used in this study is also included (green curve; peak intensity was reduced to fit the graph).

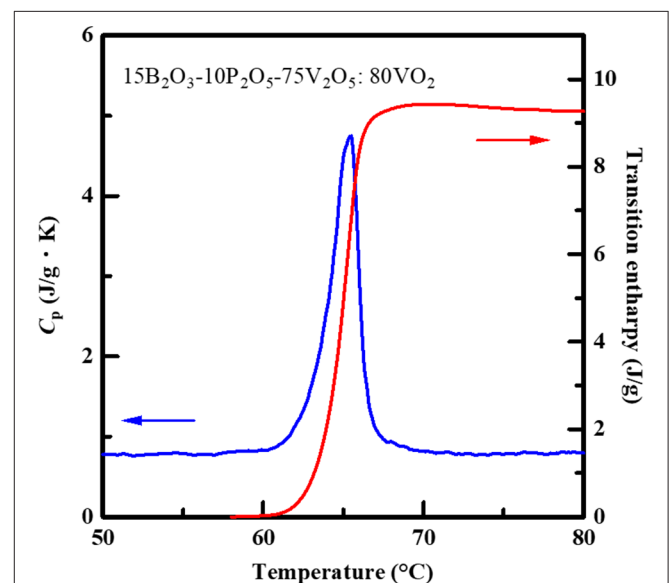


FIGURE 3 | Heat capacity and transition enthalpy for the VO₂-dispersed glass in the B₂O₃-P₂O₅-V₂O₅ system with $x = 80$. The transition enthalpy, ΔH , was obtained by thermodynamic treatment based on $H = \int C_p dT$ because the enthalpy corresponded to the latent heat storage capacity.

to be due to low dispersion of incorporated VO₂ phase in the matrix glass.

Thermal Properties

We have measured the specific heat in the VO₂-dispersed glass with $x = 80$ as a representative sample by means of DSC measurement in order to examine the latent heat storage function. A steep change in the specific heat (peak of the C_p - T curve), related to the phase transition of the dispersed VO₂ powder, was observed around the phase-transition temperature of VO₂ as well as the DTA result, and subsequently, the transition enthalpy (ΔH ; the latent heat storage capacity) was estimated to be $\Delta H \sim 9.5$ J/g (Figure 3), corresponding to ca. 21% of that of the VO₂ reagent, i.e., ~ 45 J/g (Muramoto et al., 2018). Thus, the latent heat storage function is also demonstrated in the dispersed sample in this study. Furthermore, the ΔH value obtained in this study is larger than the value of the VO₂-dispersed sample with same amount of VO₂, i.e., $\Delta H = 8.9$ J/g for the 30BaO-10TeO₂-60V₂O₅:80VO₂ (Muramoto et al., 2018).

DISCUSSION

Vanadate-system glasses are recognized to be synthesized at low melting-process temperature compared to the usual silicate glass. This is quite important for fabrication of the VO₂-dispersed glass in order to prevent the degradation/decomposition of dispersed VO₂ phase due to its transforming into other oxide phases, e.g., Magneli phase (Baldassarre et al., 2007), and to energy saving during the fabrication process. The thermal assessment in this study revealed that, apart from the problem of low water resistivity, the studied B₂O₃-P₂O₅-V₂O₅ system is able to involve the VO₂ powder and to allow its phase transition, which provides a latent heat storage function. In addition, the T_g of the studied glass matrix is lower than that of matrix previously studied; $T_g = 276^\circ\text{C}$ for 30BaO-10TeO₂-60V₂O₅ glass (Muramoto et al., 2018), suggesting the re-formability of the dispersed glass after its fabrication.

Barde et al. described a weakness against water in B₂O₃-P₂O₅-V₂O₅ system glass, which is evidenced by DTA (Barde et al., 2015). It is supposed that, under low moisture conditions, the VO₂-dispersed glass in this study works as an all-solid PCM. Otherwise, the addition of other glass constituents, which contributes to the improvement of water resistivity, also seems to be effective for the PCM application because Kubiki et al. reported that the addition of WO₃ provides the strengthening of

the glass network in vanadate-system glass, resulting in its high chemical durability (Kubiki et al., 2013). In addition, another point that should be improved is the dispersibility of VO₂ in a glass matrix. The SEM result (Figure 1B) suggests that the VO₂ particles are inhomogeneously dispersed in the matrix glass because the size of inclusion is ca. 100 μm despite the size of the VO₂ particle being estimated to be ~ 20 μm (Muramoto et al., 2018), i.e., aggregation of VO₂ particles. Irradiation of the ultrasonic wave during the incorporation process may be effective to obtain a well-dispersed sample.

SUMMARY

We already have proposed a new all-solid PCM, i.e., VO₂-dispersed glass, and demonstrated the latent heat storage in the BaO-TeO₂-V₂O₅ system. In this study, to avoid the use of Te element, which is a rare metal and is toxic, another candidate vanadate system was considered, i.e., the B₂O₃-P₂O₅-V₂O₅ system, as a matrix glass. We have been able to fabricate the VO₂-dispersed glasses in this system and demonstrated the heat storage function due to the structural phase transition of VO₂. Furthermore, the latent heat storage capacity observed in the studied VO₂-dispersed sample is larger than the capacity of the sample in the BaO-TeO₂-V₂O₅ system, suggesting the potential of all-solid PCM application.

DATA AVAILABILITY STATEMENT

The datasets generated for this study are available on request to the corresponding author.

AUTHOR CONTRIBUTIONS

KM fabricated and characterized the materials. YT, NT, and TF designed the study. YY and SS contributed to the thermal analysis. and YT and TF wrote the paper.

ACKNOWLEDGMENTS

This work was supported by the Ministry of Education, Culture, Sports, Science and Technology of the Japanese government. The authors would like to thank Dr. Takamichi Miyazaki of the Department of Instrumental Analysis, Tohoku University, for significant contribution to this study.

REFERENCES

- Ahamad, M. N., Vaish, R., and Varma, K. B. R. (2012). Calorimetric studies on 2TeO₂-V₂O₅ glasses. *J. Therm. Anal. Calorim.* 105, 239–243. doi: 10.1007/s10973-011-1305-3
- Baldassarre, L., Perucchi, A., Arcangeletti, E., Nicoletti, D., Castro, D. D., Postorino, P., et al. (2007). Electrodynamics near the metal-to-insulator transition in V₃O₅. *Phys. Rev. B* 75:245108. doi: 10.1103/PhysRevB.75.245108
- Barde, R. V., Nemade, K. R., and Waghuley, S. A. (2015). AC conductivity and dielectric relaxation in V₂O₅-P₂O₅-B₂O₃ glasses. *J. Asian Ceram. Soc.* 3, 116–122. doi: 10.1016/j.jascr.2014.11.006
- Choi, S. Y., and Ryu, B. K. (2015). Nanocrystallization of vanadium borophosphate glass for improving the electrical and catalytic properties. *J. Nanomater.* 76:201597. doi: 10.1155/2015/201597
- Farid, M. M., Khudhair, A. M., Razack, S. A. K., and Al-Hallaj, S. (2004). A review on phase change energy storage: materials and applications. *Energy Convers. Manage.* 45, 1597–1615. doi: 10.1016/j.enconman.2003.09.015
- Hasnain, S. M. (1998). Review on sustainable thermal energy storage technologies, part I: heat storage materials and techniques. *Energy Convers. Manage.* 11, 1127–1138. doi: 10.1016/S0196-8904(98)00025-9
- Jacob, R., and Bruno, F. (2015). Review on shell materials used in the encapsulation of phase change materials for high temperature thermal

- energy storage. *Renew. Sust. Energy Rev.* 48, 79–87. doi: 10.1016/j.rser.2015.03.038
- Komatsu, T., Shioya, K., and Matusita, K. (1995). Fabrication of transparent tellurite glasses containing potassium niobate crystals by an incorporation method. *J. Am. Ceram. Soc.* 76, 2923–2926. doi: 10.1111/j.1151-2916.1993.tb04040.x
- Kubiki, S., Matsuda, K., Akiyama, K., Homonnay, Z., Sinkó, K., Kuzmann, E., et al. (2013). Enhancement of electrical conductivity and chemical durability of 20R₂O·10Fe₂O₃·xWO₃·(70-x)V₂O₅ glass (R=Na, K) caused by structural relaxation. *J. Non-Cryst. Solids* 378, 227–233. doi: 10.1016/j.jnoncrysol.2013.07.012
- Muramoto, K., Takahashi, Y., Terakado, N., Yamazaki, Y., Suzuki, S., and Fujiwara, T. (2018). VO₂-dispersed glass: a new class of phase change material. *Sci. Rep.* 8:2275. doi: 10.1038/s41598-018-20519-6
- Niitaka, S., Takagi, H., and Miyano (2010). Japan Patent Kokai 2010-163510.
- Nomura, T., Tsubota, M., Okinaka, N., and Akiyama, T. (2015a). Improvement on heat release performance of direct-contact heat exchanger using phase change material for recovery of low temperature exhaust heat. *ISIJ Int.* 55, 441–447. doi: 10.2355/isijinternational.55.441
- Nomura, T., Zhu, C., Sheng, N., Saito, G., and Akiyama, T. (2015b). Microencapsulation of metal-based phase change material for high-temperature thermal energy storage. *Sci. Rep.* 5:9117. doi: 10.1038/srep09117
- Sakamoto, A., and Yamamoto, S. (2010). Glass-ceramics: engineering principles and applications. *Int. J. Appl. Glass Sci.* 1, 237–247. doi: 10.1111/j.2041-1294.2010.00027.x
- Tokoro, H., Yoshikiyo, M., Imoto, K., Namai, A., Nasu, T., Nakagawa, K. et al. (2015). External stimulation-controllable heat-storage ceramics. *Nat. Commun.* 6:7037. doi: 10.1038/ncomms8037
- Wu, C., Zhang, X., Dai, J., Yang, J., Wu, Z., Wei, S., et al. (2011). Direct hydrothermal synthesis of monoclinic VO₂(M) single-domain nanorods on large scale displaying magnetocaloric effect. *J. Mater. Chem.* 21, 4509–4517. doi: 10.1039/c0jm03078c

Conflict of Interest: The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Copyright © 2020 Muramoto, Takahashi, Terakado, Yamazaki, Suzuki and Fujiwara. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.